

Technical Information for Performance Solutions

Topics:

- Formulating with Millathane® Millable Polyurethanes
- Millathane Grade Choice
- Cure Systems
- Antioxidants
- Fillers
- Plasticizers
- Process Aids
- Ingredients to Avoid
- Ask Dr. Millathane

Formulating with Millathane® Millable Polyurethanes

Millable polyurethanes are generally compounded similar to other types of rubber, but there are some factors to consider and some ingredient interactions to be aware of. This bulletin is meant to be a guideline for ingredient selection for Millathane millable polyurethanes.

Millathane Grade Choice

In deciding which grade to use, the first question is whether polyether or polyester polyurethanes are preferable. *Polyether* types are inherently better for water and hydrolysis resistance than polyester types and would generally be used for applications requiring long term water or humid environment exposure. Polyester grades, however, can be very good for moderate exposures to these conditions, with the addition of hydrolysis stabilizers like Millstab™ P.

Polyester types are better for oil, solvent, heat and compression set resistance than polyether grades, with Millathane 66 being best for heat and set resistance, and Millathane 5004 being best for oil and solvent resistance. Because all polyester polyurethanes are prone to the effects of hydrolysis, it's highly recommended that Premilled grades, which contain 1.5 phr of Millstab P, be used. Additional amounts of Millstab P can be added for improved protection.

Note that different grades of Millathane can often be blended together, to modify processing characteristics or cured properties. Examples are Millathane E34/76 blends and Millathane 5004/66 blends (TIPS V10-1 discusses the latter).

Cure Systems

All Millathane grades can be peroxide cured, and some grades can be sulfur cured. Generally, peroxide cures will give better heat and compression set resistance compared to sulfur cures, but sulfur cures will generally give higher strength (tensile and tear) properties along with better abrasion resistance. Sulfur cures are more prone to reversion upon over-curing or high temperature curing, while peroxide cures are much more resistant to reversion.

Peroxide cures — The peroxides commonly used with other rubber types will generally work well in millable polyurethanes, including DBPH and dicumyl peroxide. It's important to note that different levels of peroxides are needed for different grades. The following is a guideline to the peroxide levels that generally give the best balance of properties with different Millathane grades:

Typical levels of DCP-40 or DBPH-50	
Millathane HT	0.5 - 1.2
Millathane 97	1.2 - 2.5
Millathane CM, E34, 55, E40, 76	2 - 3
Millathane 26	4 - 5
Millathane 5004, 66	4 - 8

Coagents are commonly used in peroxide cures to modify properties. TAC or TAIC can be used at low levels (0.5-2 phr) to improve set properties, although tear strength and abrasion resistance may be diminished somewhat. Liquid methacrylates like TMPTMA (SR-350) and DEGDMA (SR-231) are commonly used, sometimes at high levels, to increase hardness and improve processing. Blends of trifunctional methacrylates (e.g., SR-350) with difunctional methacrylates (e.g., SR-231 or SR-297) give better properties in high hardness compounds than using trifunctional methacrylates alone. Liquid polybutadienes (e.g., Ricon 154, Lithene AH) can be used to plasticize and improve compression set, although these are not as effective as the methacrylates.

Sulfur cures — The original combination of MBTS, MBT, Thanecure® ZM and sulfur, developed by DuPont in the late 1950's for Adiprene C (now, Millathane CM), is still the best cure system for sulfur curable millable polyurethanes. The typical levels of these curatives now used are 4/2/1/1.5 (MBTS/MBT/Thanecure ZM/Sulfur), which gives a good combination of cure speed and physical properties. The curative levels used in most of the original DuPont work, 4/1/0.35/0.75 (sometimes referred to as the “classic” cure system) give good properties with better heat resistance than the standard curative levels, but curing needs to be done for long times (30-60 minutes) at low temperatures (140°-150°C) to get good cures. Curing compounds using the “classic” cure system at higher temperatures usually results in pock-marking in the cured samples. Zinc stearate, which functions as an activator and process aid, is also used in sulfur cure systems at 0.5 phr.

Isocyanate cures — The isocyanate cure system, a combination of Thanecure® T9SF, HQEE (finely ground), and accelerator (e.g., Bismate), can be used with several Millathane grades to achieve high hardness compounds, up to 65 Shore D, with exceptional tensile and tear strength properties and very good abrasion resistance.

Millathane 26 gives the best properties with this cure system, giving tensile strengths up to 7500 psi (52 MPa) and Tear C values up to 800 lb/in (140 kN/m). Millathane 97, Millathane 76, Millathane E34 and Millathane 55 can also be cured with this cure system, with somewhat lower, but very good, strength properties.

Important things to note in using this cure system:

- * compounds have very short shelf life. At RT, compound must be used within 24 hours. Freezer storage, at -10°C, can give 2 – 4 (or more) weeks shelf life.
- * compounds need to be mill mixed, and cured at low temperatures (120°-135°C)
- * small amounts of TDI may be generated during mixing and curing, so ventilation and PPE may be required (refer to the MSDS/SDS for Thanecure T9SF).

Antioxidants

Heat resistance of peroxide cured polyether grades (e.g., Millathane CM, E34, E40, 55, 97*, 26) will generally be improved by the addition of antioxidants. Several that have been found effective are Irganox (or Songnox) 1010, Irganox 1076 and Naugard 445. The combination of Irganox 1010 and Naugard 445, at 0.5-1.0 phr each, will be sufficient for most applications.

Antioxidants give minimal benefit to polyester Millathane grades (which are inherently better for heat resistance than polyether grades) and to sulfur cured compounds.

*A minimum of 0.25 phr antioxidant is required in *all* Millathane 97 compounds.

Fillers

For black compounds, any of the rubber carbon blacks can be used. N330 is very commonly used, as it gives a good combination of excellent properties and easy mixing. For non-black compounds, precipitated silicas (e.g., HiSil 233 or Ultrasil VN3) are very commonly used and give excellent properties. Fumed silica gives somewhat higher hardness and reinforcement than precipitated silicas, and is used for transparent compounds (of Millathane 97). Silane coupling agents (e.g., Silquest A189 for sulfur cures, Silquest RC-1 for peroxide cures) are often used with silicas to improve properties, primarily tear strength and abrasion resistance.

MILLATHANE®

FACTOID:

Millathane 55 gives lower viscosity and higher hardness (primarily in sulfur cures) than Millathane E34 (with other properties similar).

TIPS V11-1

Plasticizers

Many of the plasticizers that are used in polar rubbers like NBR can also be used in Millathane compounds. TP-95 (DBEEA) is very commonly used because it is very compatible with millable polyurethanes and gives good properties and processing. Other commonly used plasticizers are Medioplast NB4 and coumarone indene resins (e.g., Cumar P10), although the latter cannot be used in peroxide cures because they will retard curing.

Process Aids


Most compounds contain small amounts of process aids to prevent mill/mixer sticking. Sulfur cures will always have 0.5 phr of zinc stearate and peroxide cures will typically have about 0.25 phr stearic acid. Additionally, a small amount (0.5-2 phr) of process aids like Struktol WB222, Dispergator FL, and/or low melt polyethylene (AC617A) are often used.

Ingredients to Avoid

Zinc oxide — This ingredient will retard cures of millable polyurethanes, especially polyester grades like Millathane 76, where even 0.5 phr affects the curing significantly and 5 phr gives virtually no cure activity (see chart below). The effect is not as severe in polyether grades like Millathane E34, especially at low levels.

Calcium oxide will also retard curing of millable polyurethanes, and should not be used in Millathane compounds (see chart below).

Sulphenamide accelerators — These do not function well in polyurethane cure systems.

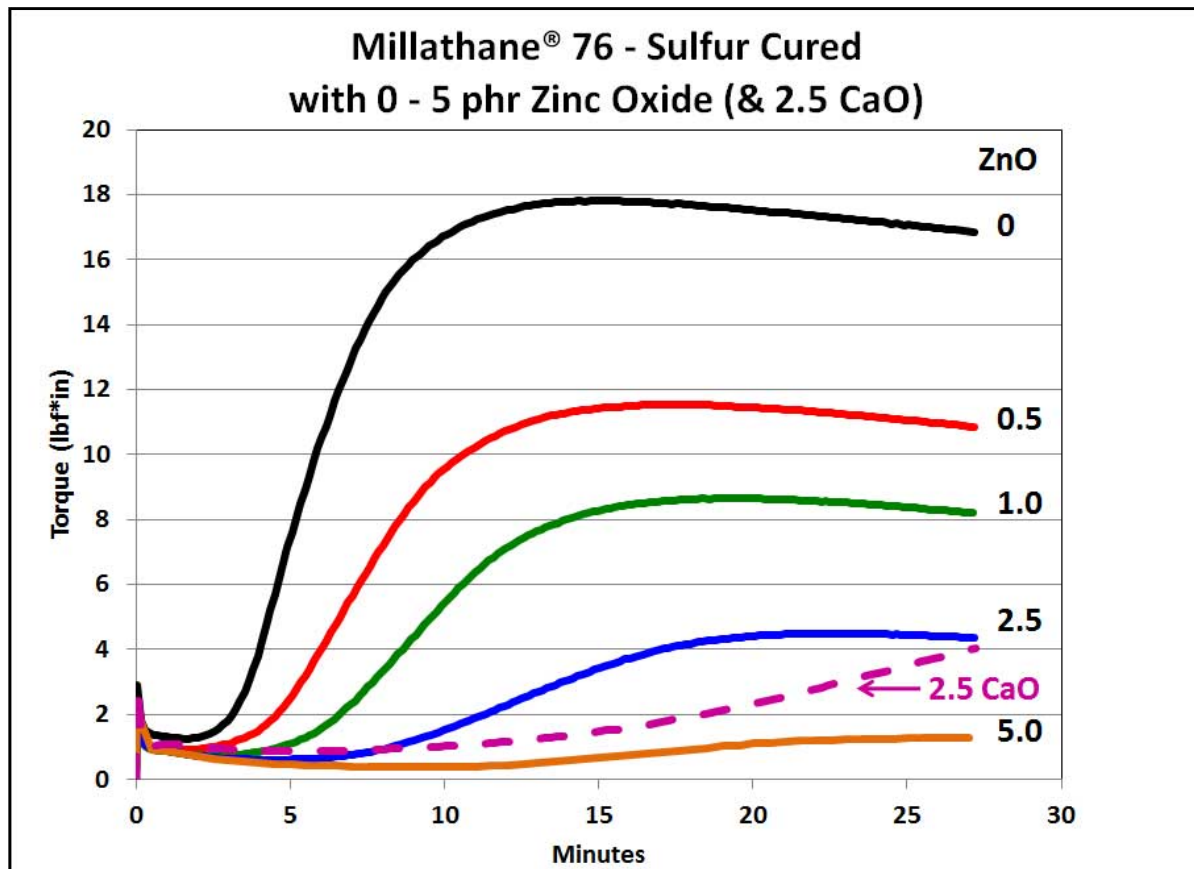

MILLATHANE®
FACTOID: The Millathane Team will be participating, with our European distributor Safic-Alcan, in the DKT/IRC 2015 Show in Nuremberg, Germany, June 29-July 2, 2015.

TSE INDUSTRIES

4370 112th Terrace North
Clearwater, FL , USA 33762-4902

Toll Free: 800-237-7634
Phone: 727-573-7676
Fax: 727-572-0487
E-mail: millathaneinfo@tse-industries.com



www.tse-industries.com

Technology / Service /
Experience

An ISO 9001:2000
Certified Company

We are here to serve you:

Tom Jablonowski, <i>Technical Service Manager</i>	tom.jablonowski@tse-industries.com
Nina Manee, <i>Sales & Marketing Representative</i>	nina.manee@tse-industries.com
Massimo Cerboni, <i>Global Business Director</i>	massimo.cerboni@tse-industries.com

**ASK Doctor Millathane®**

Dear Dr. Millathane,

Can I make a black (or other color) masterbatch out of Millathane millable polyurethane?
Butch

Dear Mr. Butch,

Yes, color masterbatches can be made with Millathane polymers, but preferably out of polyether grades like E34 or 55, which will have better shelf life than polyester grades. If a polyester grade is used (like Millathane 76), it's preferable to use a Premilled grade, which contains 1.5 phr of hydrolysis stabilizer (Millstab™ P), to give the masterbatch better hydrolysis resistance and shelf life. Polyester urethane masterbatches should be used within one year, polyether urethane batches within 3 years, stored in cool, dry conditions.

Good Luck!

Dr. Millathane

If you have any Millathane millable urethane questions you'd like answered, please send an email to millathaneinfo@tse-industries.com.